

OCELE PRE PRÁCU ZA STUDENA

Dostupné výrobné profily

[Tyčové polotovary*](#)
[Plechý](#)

*) Presented data refer exclusively to long products. Please observe the detailed explanations at the end of the data sheet (pdf).

Popis produktu

BÖHLER K107 is a 12% ledeburitic chromium steel and corresponds to material number 1.2436 (X210CrW12). Due to the higher tungsten content, BÖHLER K107 achieves a higher resistance to abrasive wear compared to the conventional tool steel 1.2080. Compared to modern cold work tool steels, BÖHLER K107 has the advantage of simple heat treatment with lower hardening temperatures and single tempering. However, this characteristic tempering behaviour limits the use of modern coatings..

Spôsob výroby

[Konvenčná výroba](#)

Vlastnosti

> Odolnosť proti opotrebovaniu : dobré

Aplikácia

- > Strojové nože (pre výrobcov)
- > Valcovanie
- > Tvárnenie za studena
- > Strihanie / Dierovanie / Lisovanie / Presné strihanie
- > Výroba normalizovaných dielov (strižníky, platne, kolíky, razníky)
- > Komponenty pre recykláciu
- > Oteruvzdorné diely
- > Diely pre všeobecné strojárstvo

Technické údaje

Označenie materiálu	Normy
1.2436 SEL	4957 EN ISO
X210CrW12 EN	
~ D6 AISI	

Chemické zloženie

C	Si	Mn	Cr	W
2,10	0,25	0,40	11,50	0,70

Porovnanie vlastnosti materiálu

	Odolnosť proti tlakovému zaťaženiu	Rozmerová stabilita počas tepelného spracovania	Húževnatosť	Odolnosť proti abrazívnemu opotrebovaniu	Odolnosť proti adhezívnemu opotrebovaniu
BÖHLER K107	★★	★★	★	★★★	★★
BÖHLER K100	★★	★★	★	★★★	★★
BÖHLER K105	★★	★★	★	★★	★★
BÖHLER K110	★★	★★★	★	★★★	★★
BÖHLER K190 MICROCLEAN®	★★★★★	★★★★★	★★★★★	★★★★★	★★★★★
BÖHLER K294 MICROCLEAN®	★★★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K340 ECOSTAR®	★★★	★★★	★★	★★	★★
BÖHLER K340 ISODUR®	★★★	★★★★★	★★★	★★★	★★★★★
BÖHLER K346	★★★	★★★	★★★	★★★★★	★★
BÖHLER K353	★★	★★★	★★	★★	★★
BÖHLER K360 ISODUR®	★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K390 MICROCLEAN®	★★★★★	★★★★★	★★★★★	★★★★★	★★★★★
BÖHLER K490 MICROCLEAN®	★★★★★	★★★★★	★★★★★	★★★★★	★★★★★
BÖHLER K497 MICROCLEAN®	★★★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K888 MATRIX	★★★★★	★★★★★	★★★★★	★★	★★
BÖHLER K890 MICROCLEAN®	★★★★★	★★★★★	★★★★★	★★★	★★★

Stav pri dodaní
Žihany

Tvrdosť (HB)	max. 250
--------------	----------

Tepelné spracovanie
Žihanie

Teplota	800 až 850 °C	Slow controlled cooling in furnace at a rate of 50 - 68°F/hr (10 to 20°C/hr) down to approx. 1112°F (600°C), further cooling in air.
---------	---------------	--


Žihanie na odstránenie prnutí

Teplota	650 až 700 °C	Slow cooling in furnace. Intended to relieve stresses set up by extensive machining, or in complex shapes. After through heating, hold in neutral atmosphere for 1 - 2 hours
---------	---------------	--

Kalenie a popúšťanie

Teplota	950 až 980 °C	Oil, salt bath 428 to 482°F or 932 to 1022°F (220 to 250°C or 500 to 550°C), air plast, still air, gas; Holding time after temperature equalization: 15 to 30 minutes. Special treatment: Hardening 1868°F (1020°C) and tempering at 932°F (500°C). After hardening, tempering to the desired working hardness, see tempering chart.
---------	---------------	--

Tempering chart

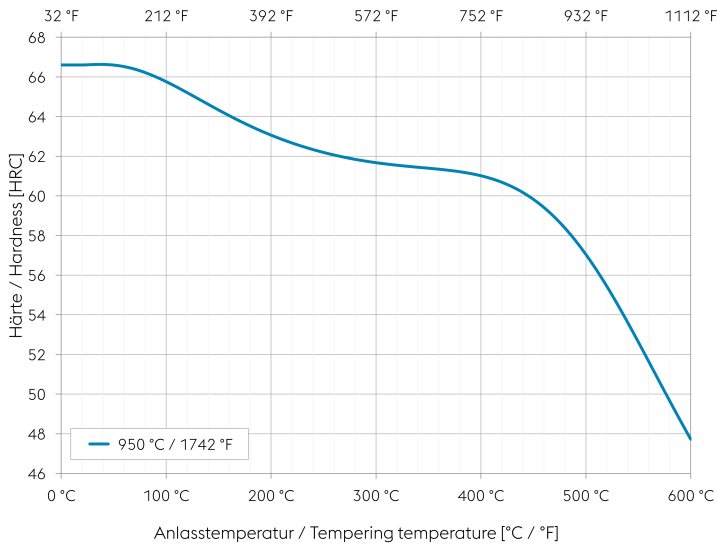

Tempering:

Specimen size: square 0,787 inch (20 mm)

Slow heating to tempering temperature immediately after hardening.


Time in furnace 1 hour for each 0,787 inch (20 mm) of workpiece thickness but at least 2 hours/cooling in air.

Slow cooling to room temperature after each tempering step is recommended.

Please refer to the tempering chart for guide values for the hardness achievable after tempering.

Tempering for stress relieving 86 to 122 °F (30 to 50 °C) below the highest tempering temperature.

Continuous cooling CCT curves

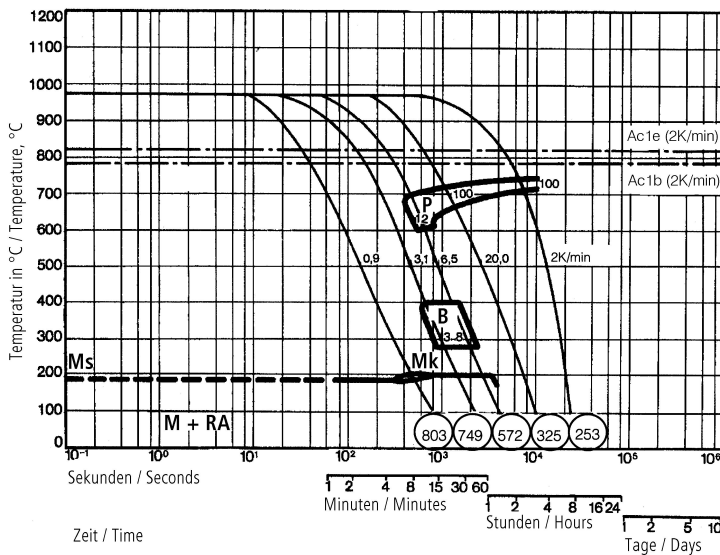

Austenitising temperature: 1796°F (980°C)
Holding time: 30 minutes

O Vickers hardness

3...100 phase percentages

0.9...20.0 cooling parameter, i.e. duration of cooling


from 1472 to 932°F (800 to 500°C) in $s \times 10^{-2}$

35,6°F/min (2 K/min) cooling rate in °F/min (K/min) in

the 1472 to 932°F (800 to 500°C) range

Mk... Grain boundary martensite

Quantitative phase diagram

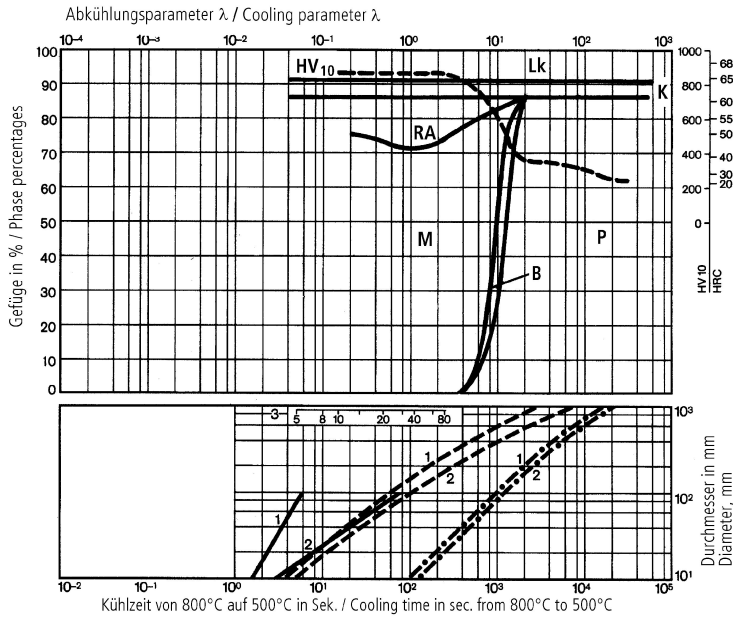


Lk... Ledeburite carbide
 RA... Residual austenite
 A... Austenite
 B... Bainite
 P... Perlite
 K... Carbide
 M... Martensite

— Water cooling
 - - - Oil cooling
 - · - Air cooling

1... Edge or face
 2... Core
 3... Jominy test: distance from end


Isothermal TTT curves

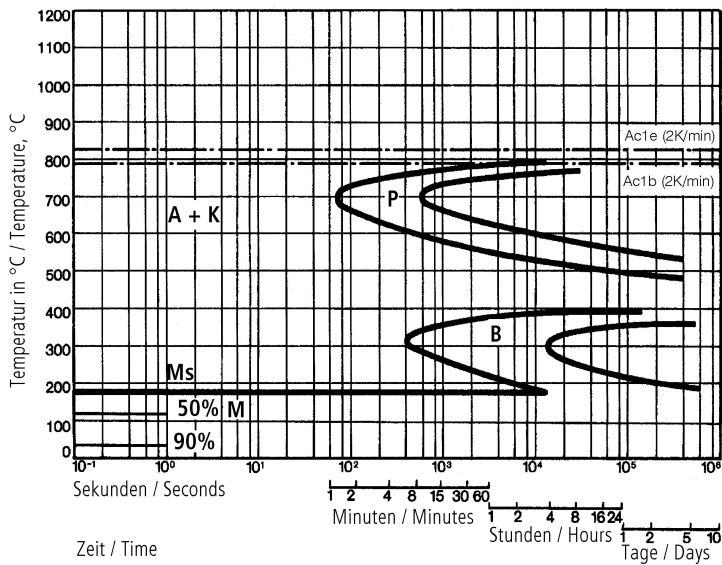


Austenitising temperature: 980°C / 1796°F
 Holding time: 30 minutes

A... Austenite
 B... Bainite
 P... Pearlite
 K... Carbide
 M... Martensite

Influence of work diameter on core hardness and hardness penetration

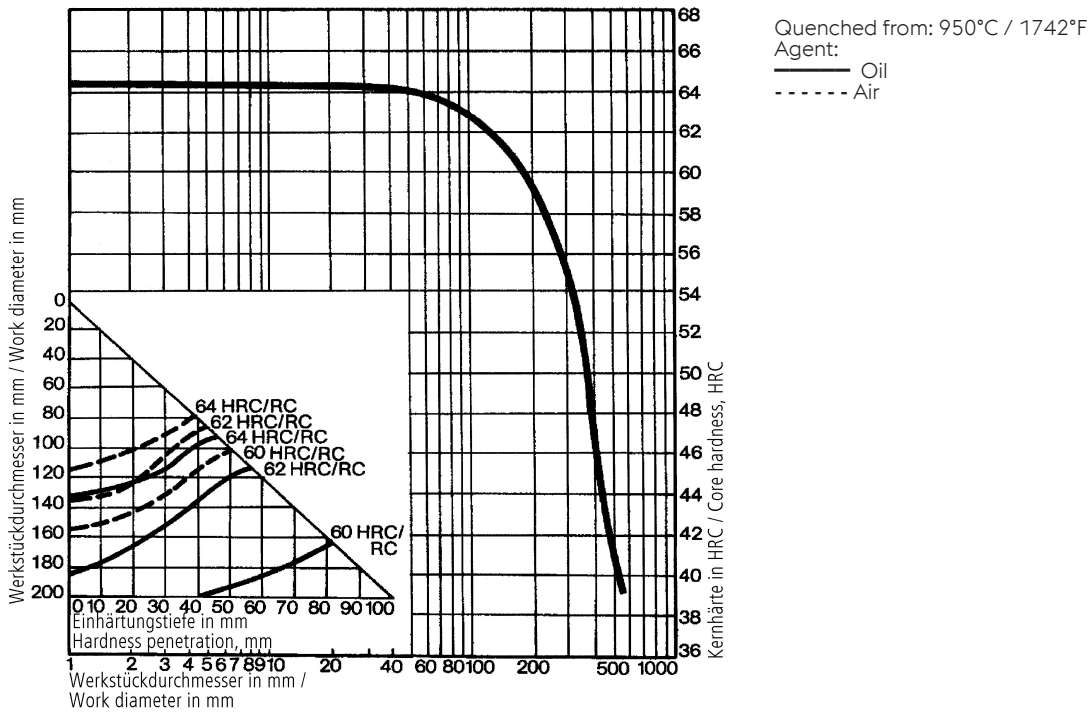

Heat treatment sequence

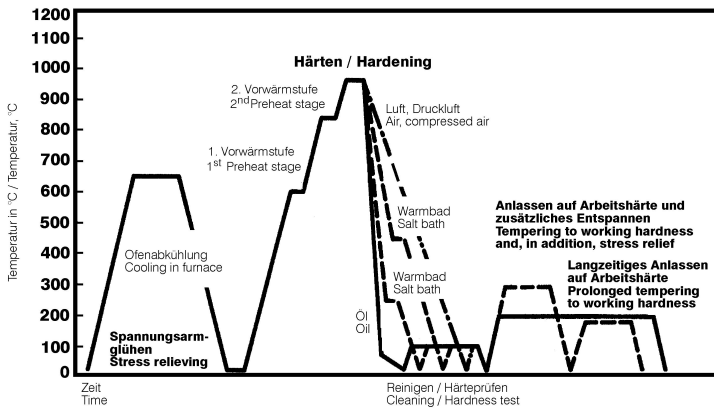

Fyzikálne vlastnosti

Teplota (°C)	20
Hustota (kg/dm ³)	7,7
Tepelná vodivosť (W/(m.K))	20
Merná tepelná kapacita (kJ/kg K)	0,46
Merný elektrický odpor (Ohm.mm ² /m)	0,65
Modul pružnosti (10 ³ N/mm ²)	210

Tepelná rozťažnosť

Teplota (°C)	100	200	300	400	500	600
Tepelná rozťažnosť (10 ⁻⁶ m/(m.K))	10,5	11	11	11,5	12	12

Long Products: For additional specifications and technical requirements, please contact our regional voestalpine BÖHLER sales companies.

Sheet & Plates: Product Variant may differ in terms of melting process, technical data, delivery, and surface condition as well as available product dimensions. Please contact voestalpine BÖHLER Bleche GmbH & Co KG.

The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.